

## Advanced Materials

<b>Araldite®</b>	<b>CY 205 IN</b>	<b>100</b>	<b>pbw</b>
<b>Aradur®</b>	<b>HY 905 IN</b>	<b>100</b>	<b>pbw</b>
<b>Flexibilizer</b>	<b>DY 040</b>	<b>0 - 20</b>	<b>pbw</b>
<b>Accelerator</b>	<b>DY 061</b>	<b>0.2 - 1</b>	<b>pbw</b>
<b>Filler</b>	<b>Silica Flour</b>	<b>310 - 430</b>	<b>pbw</b>

Liquid, hot-curing casting resin system for producing castings with good electrical and mechanical end-properties.

### Application

Indoor electrical insulators for medium and high voltage, such as post insulators, bushings, switch and apparatus components as well as instrument transformers and dry type distribution transformers.

### Processing Methods

Conventional gravity casting process under vacuum.

Adjustable to existing handling parameters.

### Key Properties

Good mechanical and electrical end properties

Very high thermal endurance properties

Considerable insensitivity to atmospheric and chemical influences.

## Product Data (Guideline Values)

<b>Araldite CY 205 IN</b>	Liquid, solvent-free, unmodified Bisphenol A epoxy resin.				
Viscosity	at 25 °C	ISO 12058-1	mPa s	9000 – 13000*	
Epoxy content		ISO 3001	equiv/kg	5.21 - 5.49*	
Density	at 25 °C	ISO 1675	g/cm <sup>3</sup>	1.15 - 1.20>	
Flash point		ISO 1523	°C	200	
Vapour pressure	at 20 °C	(Knudsen)	Pa	< 0.01	
	at 60 °C	(Knudsen)	Pa	appr. 1	

<b>Aradur HY 905 IN</b>	Liquid, modified, carboxylic anhydride curing agent.				
Viscosity	at 25 °C	ISO 12058-1	mPa s	150 – 250*	
Density	at 25 °C	ISO 1675	g/cm <sup>3</sup>	1.18 - 1.22	
Flash point		ISO 1523	°C	150	
Vapour pressure	at 20 °C	(Knudsen)	Pa	appr. 0.3	
	at 60 °C	(Knudsen)	Pa	appr. 50	

<b>Flexibilizer DY 040</b>	Low viscous, solvent-free Polyglycol.				
Viscosity	at 25 °C	ISO 12058-1	mPa s	60 – 90*	
Density	at 25 °C	ISO 1675	g/cm <sup>3</sup>	1.02 - 1.04	
Flash point		ISO 1523	°C	> 100	
Vapour pressure	at 20 °C	(Knudsen)	Pa	appr. 0.03	
	at 60 °C	(Knudsen)	Pa	appr. 1	

<b>Accelerator DY 061</b>	Solvent-free tertiary amine				
Viscosity	at 25 °C	ISO 12058-1	mPa s	1000 – 1800*	
Density	at 25 °C	ISO 1675	g/cm <sup>3</sup>	0.97 – 1.02	
Flash point		ISO 1523	°C	> 100	
Vapour pressure	at 20 °C	(Knudsen)	Pa	appr. 1	
	at 60 °C	(Knudsen)	Pa	appr. 50	

\*Specified range

**Remarks** Hardener Aradur HY 905 IN is sensitive to humidity and tends at low storage temperature to crystallize. It can be reliquefied by stirring and heating it to 40 - 80 °C.

**Storage** Store the components in a dry place according to the storage conditions stated on the label in tightly sealed original containers. Under these conditions, the shelf life will correspond to the expiry date stated on the label. After this date, the product may be processed only after reanalysis. Partly emptied containers should be tightly closed immediately after use.  
For information on waste disposal and hazardous products of decomposition in the event of a fire, refer to the Material Safety Data Sheets (MSDS) for these particular products.

# Processing (Guideline Values)

## System Preparation

### General instructions for preparing liquid resin systems

Long pot life is desirable in the processing of any casting resin system. Mix all of the components together very thoroughly at room temperature or slightly above and under vacuum. Intensive wetting of the filler is extremely important. Proper mixing will result in:

- better flow properties and reduced tendency to shrinkage
- lower internal stresses and therefore improved mechanical properties on object
- improved partial discharge behaviour in high voltage applications.

For the mixing of medium- to high viscous casting resin systems and for mixing at lower temperatures, we recommend special thin film degassing mixers that may produce additional self-heating of 10-15 K as a result of friction. For low viscous casting resin systems, conventional anchor mixers are usually sufficient.

In larger plants, two premixers are used to mix the individual components (resin, hardener) with the respective quantities of fillers and additives under vacuum. Metering pumps then feed these premixes to the final mixer or a continuous mixer. The individual premixes can be stored at elevated temperature (about 60°C) for up to about 1 week, de-pending on formulation.

Note: A premix of accelerator with resin is not stable; a premix of accelerator with hardener is stable under certain conditions. Please contact our staff for details

Mixing time can vary from 0.5 to 3 hours, depending on mixing temperature, quantity, mixing equipment and the particular application. The required vacuum is 0.5 to 5 mbar. The vapour pressure of the individual components should be taken into account.

In the case of dielectrically highly stressed parts, we recommend checking the quality consistency and predrying of the filler. Their moisture content should be  $\leq 0.2\%$ .

### Specific instructions

The effective pot-life of the mix is about 1 day at temperatures below 25°C. Conventional batch mixers should be cleaned once a week or at the end of work. For longer interruptions of work, the pipes of the mixing and metering installations have to be cooled and cleaned with the resin component to prevent sedimentation and/or undesired viscosity increase. Interruptions over a week-end (approx. 48h) without cleaning are possible if the pipes are cooled at temperatures below 18°C.

In case to use mixtures with high reactivity, we recommend to clean daily with the flexibilizer DY 040.

Viscosity increase and gel time at various temperatures, refer to Figs: 4.1 and 4.4.

### Mould temperature

Conventional vacuum casting 80 - 100°C

### Demoulding times (depending on mould temperature and casting volume)

Conventional vacuum casting 6 - 12h

### Cure conditions (minimal postcure)

Conventional Vacuum Casting 6h at 80°C + 10h at 130°C or  
6h at 80°C + 6h at 140°C

Castings with big volume (exothermic reaction, internal mechanical stresses) or encapsulations of heat sensitive active parts could be cured at appr. 80°C.

To determine whether crosslinking has been carried to completion and the final proper-ties are optimal, it is necessary to carry out relevant measurements on the actual object or to measure the glass transition temperature (T<sub>g</sub>). Different gelling and cure cycles in the manufacturing process could lead to a different crosslinking and glass transition temperature respectively.

# Processing Data (Guideline Values)

System tested:  
 Araldite CY 205 IN / HY 905 IN/ DY 040 / DY 061 / Silica.  
 Mix ratio: 100 / 100 / 10 / 1 / 410.

## Processing Viscosities

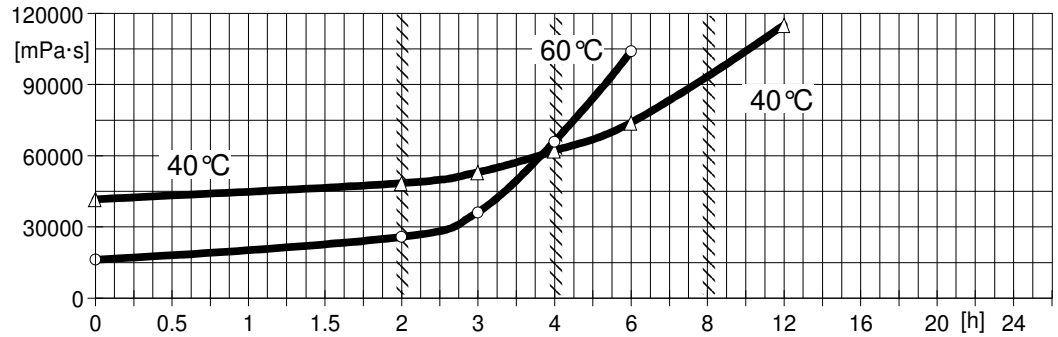


Fig.4.1: **Viscosity increase at 40 and 60°C** (measurements with Rheomat 115)  
 (Shear rate  $D = 10 \text{ s}^{-1}$ )

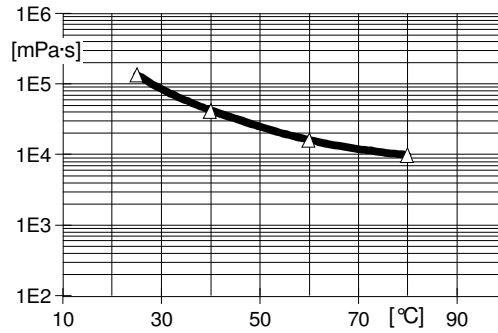


Fig.4.2: **Initial viscosity as a function of temperature**  
 (measurements with Rheomat 115,  $D = 10 \text{ s}^{-1}$ )

## Gelation-/Cure Times

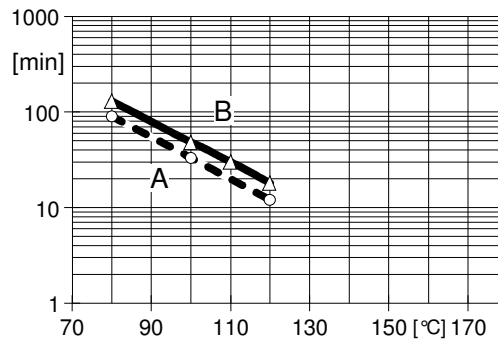


Fig.4.4: **Geltime measured with Gelnorm Instrument as a function of temperature**  
 (ISO 9396)  
 A = 1 pbw DY 061 / B = 0.5 pbw DY 061.

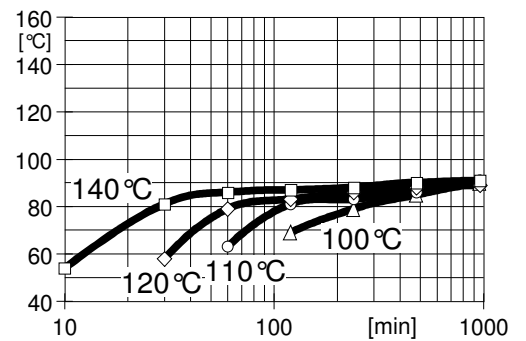


Fig.4.5: **Glass transition temperature as a function of the cure time**  
 (isothermic reaction, ISO 11357-2)

# Mechanical and Physical Properties (Guideline Values)

Araldite CY 205 IN / HY 905 IN / DY 040 / DY 061 / Silica.  
 Mix ratio: 100 / 100 / 10 / 1 / 410, cured for 6h at 80°C + 10h at 130°C.  
 Determined on standard test specimen at 23°C.

Tensile strength	ISO 527	MPa	75 - 85
Elongation at break	ISO 527	%	0.9 - 1.1
E modulus from tensile test	ISO 527	MPa	12000 - 13000
Flexural strength	ISO 178	MPa	125 - 135
Surface strain	ISO 178	%	1.1 - 1.5
E modulus from flexural test	ISO 178	MPa	11600 - 12000
Compressive strength	ISO 604	MPa	140 - 150
Compression set	ISO 604	%	6 - 7
Impact strength	ISO 179	kJ/m <sup>2</sup>	10 - 12
Double Torsion Test	CG 216-0/89		
Critical stress intensity factor (K <sub>1C</sub> )		MPa·m <sup>1/2</sup>	2.7 - 2.9
Specific energy at break (G <sub>1C</sub> )		J/m <sup>2</sup>	570 - 620
Martens temperature	DIN 53458	°C	80 - 90
Glass transition temperature (DSC)	ISO 11357-2	°C	85 - 95
Coefficient of linear thermal expansion	ISO 11359-2		Fig. 5.2
Mean value for temperature range: 20 - 60°C		K <sup>-1</sup>	31 - 36·10 <sup>-6</sup>
Thermal conductivity similar to	ISO 8894-1	W/mK	0.8 - 0.9
Glow resistance	DIN 53459	class-	2b
Flammability		UL 94	
Thickness of specimen: 4 mm		class	HB
Thickness of specimen: 12 mm		class	V1
Thermal endurance profile (TEP)	IEC 60216		Fig.7.1 - 7.2
Temperature index (TI): weight loss (20000h/5000h)		°C	164 / 187
Thermal ageing class (20000h)	IEC 60085	class	F
Water absorption (specimen: 50x50x4 mm)	IEC 60062		
10 days at 23°C		% by wt.	0.10 - 0.20
60 min at 100°C		% by wt.	0.10 - 0.20
Decomposition temperature (heating rate: 10K/min)	DTA	°C	> 350
Density (Filler load: 66 % by wt.)	ISO 1183	g/cm <sup>3</sup>	1.80 - 1.90

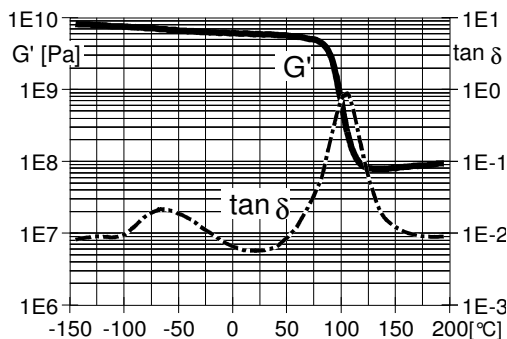


Fig.5.1: **Shear modulus (G')** and **mechanical loss-factor (tan  $\delta$ )** as a function of **temperature** (measured at 1 Hz.)  
 (ISO 6721-7, method C)

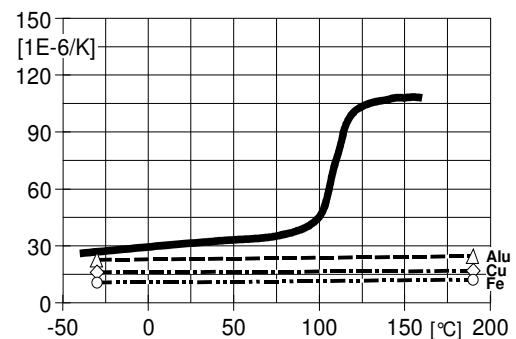


Fig.5.2: **Coefficient of linear thermal expansion ( $\alpha$ )** as a function of **temperature**  
 (ISO 11359-2, reference temperature: 23°C)

# Electrical Properties (Guideline Values)

System tested:

Araldite CY 205 IN / HY 905 IN / DY 040 / DY 061 / Silica.

Mix ratio: 100 / 100 / 10 / 1 / 410.

Determined on standard test specimen at 23°C.

Cured for 6h at 80°C + 10h at 130°C.

Breakdown strength	IEC 60243-1	kV/mm	18 - 22
Breakdown strength embedded Rogowski electrodes ( $\varnothing = 25$ mm, 2 mm gap)	Huntsman method	kV/mm	36 - 41
Diffusion breakdown strength Temperature of specimen after test	DIN/ VDE 0441/1	class °C	HD 2 23
HV arc resistance	IEC 61621	s	185 - 195
Tracking resistance with test solution A with test solution B			CTI >600-0.0 CTI >600M-0.0
Electrolytic corrosion	IEC 60426	grade	A-1

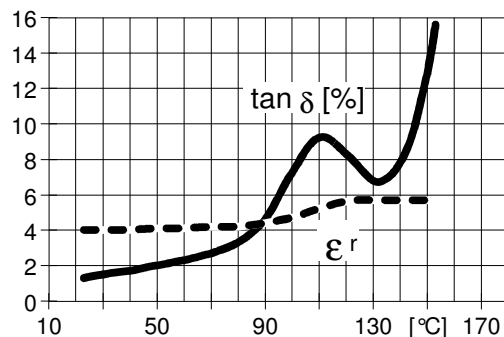


Fig.6.1: **Loss factor ( $\tan \delta$ ) and dielectric constant ( $\epsilon_r$ ) as a function of temperature**  
measurement frequency: 50 Hz,  
IEC 60250/ DIN 53483)

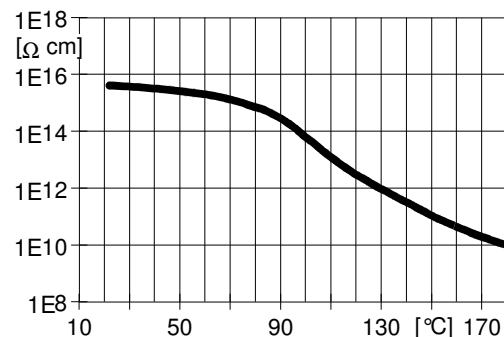


Fig.6.2: **Volume resistivity ( $\rho$ ) versus function of temperature**  
(measurement voltage: 1000 V,  
IEC 60093/ DIN 53482)

# Special Properties (Guideline Values)

System tested:  
 Araldite CY 205 / Aradur HY 905 / DY 040 / DY 061 / Silica  
 Mix ratio: 100 / 100 / 10 / 1 / 410

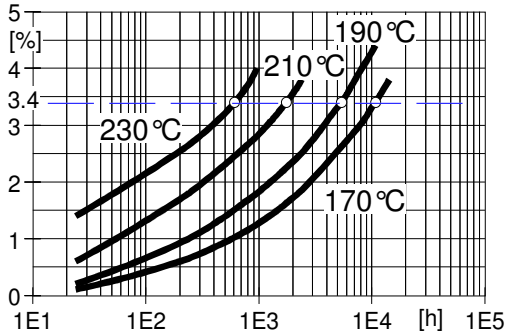


Fig.7.1: **Weight loss** (specimen: 50x50x3 mm)  
 (limit: 3.4%)

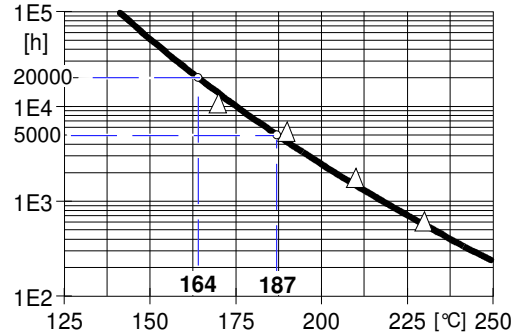


Fig.7.2: **TI 164 / 187** (weight loss 3.4%)  
 (Araldite F/Aradur HY 905/ DY 040/ DY 061/ SiO<sub>2</sub>  
 100/ 100/ 20/ 1/ 430 pbw)

**Thermal Endurance  
 Profile IEC 60216**

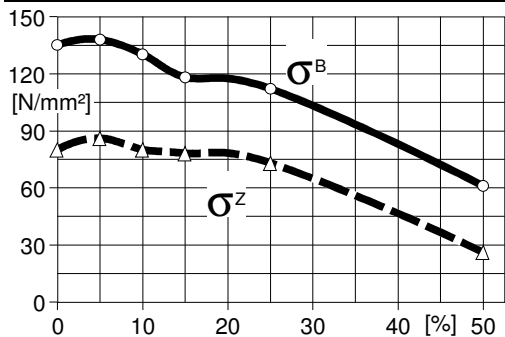


Fig.7.3: **Tensile strength ( $\sigma_z$ ) (ISO R 527)  
 and**  
 Flexural strength ( $\sigma_B$ ) (ISO 178) at  
 23°C with different parts (%) of Flexibilizer DY 040.

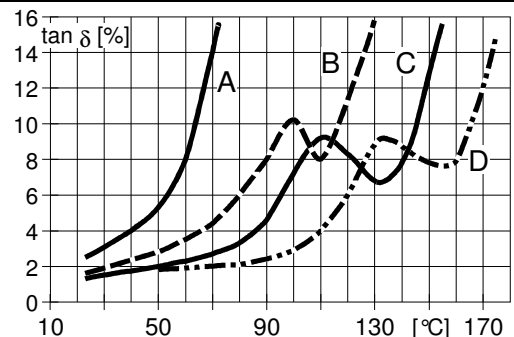


Fig.7.4: **Loss factor (tan  $\delta$ ) in f (T) with:**  
 A=25, B=20, C=10, D=0 % of Flex.  
 DY 040  
 IEC 60250 (measurement frequency: 50 Hz)

**Influence of  
 Flexibilizer DY 040**

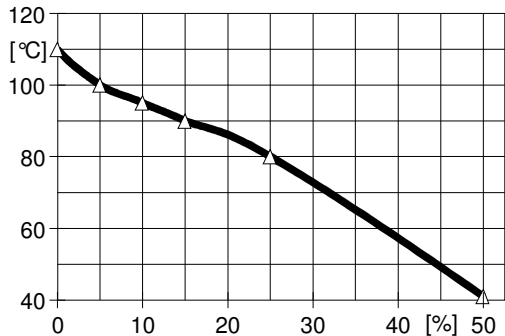


Fig.7.5: **Glass transition temperature**

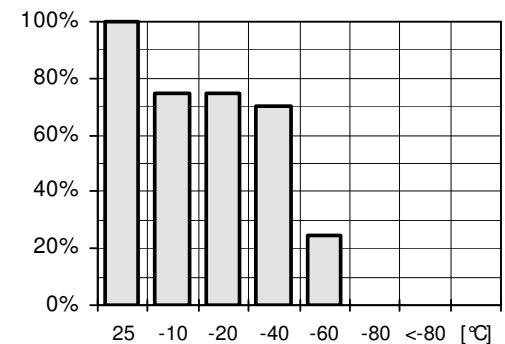


Fig.7.5: **Crack resistance / Temperature  
 shock test**  
 Passed specimen (%) as a function of the  
 temperature steps  
 Mean failure temperature: - 49°C  
 Embedded metal parts with 2 mm radius

**Thermal Shock  
 Resistance**

# Legal Notice

## Huntsman Advanced Materials

(Switzerland) GmbH  
Klybeckstrasse 200  
4057 Basel  
Switzerland

Tel: +41 (0)61 299 11 11  
Fax: +41 (0)61 299 11 12

[www.huntsman.com/advanced\\_materials](http://www.huntsman.com/advanced_materials)  
Email:  
[advanced\\_materials@huntsman.com](mailto:advanced_materials@huntsman.com)



Huntsman Advanced Materials warrants only that its products meet the specifications agreed with the user. Specified data are analysed on a regular basis. Data which is described in this document as 'typical' or 'guideline' is not analysed on a regular basis and is given for information purposes only. Data values are not guaranteed or warranted unless if specifically mentioned.

The manufacture of materials is the subject of granted patents and patent applications; freedom to operate patented processes is not implied by this publication. While all the information and recommendations in this publication are, to the best of Huntsman Advanced Material's knowledge, information and belief, accurate at the date of publication, nothing herein is to be construed as a warranty, whether express or implied, including but without limitation, as to merchantability or fitness for a particular purpose. In all cases, it is the responsibility of the user to determine the applicability of such information and recommendations and the suitability of any product for its own particular purpose.

The behaviour of the products referred to in this publication in manufacturing processes and their suitability in any given end-use environment are dependent upon various conditions such as chemical compatibility, temperature, and other variables, which are not known to Huntsman Advanced Materials. It is the responsibility of the user to evaluate the manufacturing circumstances and the final product under actual end-use requirements and to adequately advise and warn purchasers and users thereof.

Products may be toxic and require special precautions in handling. The user should obtain Safety Data Sheets from Huntsman Advanced Materials containing detailed information on toxicity, together with proper shipping, handling and storage procedures, and should comply with all applicable safety and environmental standards.

Hazards, toxicity and behaviour of the products may differ when used with other materials and are dependent on manufacturing circumstances or other processes. Such hazards, toxicity and behaviour should be determined by the user and made known to handlers, processors and end users.

Except where explicitly agreed otherwise, the sale of products referred to in this publication is subject to the general terms and conditions of sale of Huntsman Advanced Materials LLC or of its affiliated companies including without limitation, Huntsman Advanced Materials (Europe) BVBA, Huntsman Advanced Materials Americas Inc., Huntsman Advanced Materials (UAE) FZE, Huntsman Advanced Materials (Guangdong) Company Limited, and Huntsman Advanced Materials (Hong Kong) Ltd.

Huntsman Advanced Materials is an international business unit of Huntsman Corporation. Huntsman Advanced Materials trades through Huntsman affiliated companies in different countries including but not limited to Huntsman Advanced Materials LLC in the USA and Huntsman Advanced Materials (Europe) BVBA in Europe.

All trademarks mentioned are either property of or licensed to Huntsman Corporation or an affiliate thereof in one or more, but not all, countries.

Copyright © 2012 Huntsman Corporation or an affiliate thereof. All rights reserved.